

International Cotton Advisory Committee



CSITC Global - Round Trial 2021 - 2 General Evaluation

Section One: Result Distribution Section Two: Instrument Evaluation Section Three: Within Limits Evaluation

Section One: Result Distribution

Content:

Mandatory Parameters

- -Summary Table
- -Distribution Graphs

Optional Parameters

- -Summary Table
- -Distribution Graphs

Executed By:
Faserinstitut Bremen e.V., Bremen, Germany*
USDA-AMS, Memphis, TN, USA

System Provided by: Generation 10 Limited



This report is an outcome of the Project CFC/ICAC/33 – CSITC, which benefitted from support from the Common Fund for Commodities and the European Union, partners in Commodity Development.



Global - Round Trial 2021 - 2

Inter-Instrument Averages, Inter-Instrument Variations, Typical within-instrument Variations

Micronaire										
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average			
Average of Instruments (Grubbs)			4.200	4.491	3.595	4.098				
Reference Values for Evaluation			4.200	4.491	3.595	4.098				
Number Of Instruments			95	95	95	95	95			
		SD	0.065	0.046	0.048	0.053	0.053			
Inter-Instrument Variation	based on 30 tests	CV %	1.5	1.0	1.3	1.3	1.3			
		SD	0.068	0.054	0.055	0.057	0.059			
inter-instrument variation	based on 6 tests	CV %	1.6	1.2	1.5	1.4	1.4			
		SD	0.085	0.064	0.062	0.065	0.069			
	based on single tests	CV %	2.0	1.4	1.7	1.6	1.7			
	between different days	SD	0.028	0.020	0.019	0.020	0.022			
	with each 6 tests	CV %	0.7	0.4	0.5	0.5	0.5			
Typical within-instrument Variation	between single tests	SD	0.041	0.029	0.032	0.030	0.033			
(Median)	on one day	CV %	1.0	0.7	0.9	0.7	0.8			
	between all tests	SD	0.049	0.036	0.037	0.036	0.040			
	on different days	CV %	1.2	0.8	1.0	0.9	1.0			

	Strength										
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average				
Average of Instruments (Grubbs)			32.062	24.214	25.873	22.952					
Reference Values for Evaluation			32.062	24.214	25.873	22.952					
Number Of Instruments			95	95	95	95	95				
ladan la administrativo		SD	0.731	0.730	0.624	0.737	0.705				
	based on 30 tests	CV %	2.3	3.0	2.4	3.2	2.7				
		SD	0.786	0.787	0.685	0.723	0.745				
Inter-Instrument Variation	based on 6 tests	CV %	2.5	3.2	2.6	3.1	2.9				
		SD	1.015	0.919	0.921	0.845	0.925				
	based on single tests	CV %	3.2	3.8	3.6	3.7	3.5				
	between different days	SD	0.385	0.263	0.294	0.293	0.309				
	with each 6 tests	CV %	1.2	1.1	1.1	1.3	1.2				
Typical within-instrument Variation (Median)	between single tests	SD	0.675	0.402	0.528	0.438	0.511				
	on one day	CV %	2.1	1.7	2.0	1.9	1.9				
	between all tests	SD	0.753	0.478	0.591	0.501	0.581				
	on different days	CV %	2.3	2.0	2.3	2.2	2.2				

	L	ength					
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average
Average of Instruments (Grubbs)			1.1967	1.0150	1.0841	0.9994	
Reference Values for Evaluation			1.1967	1.0150	1.0841	0.9994	
Number Of Instruments			95	95	95	95	95
		SD	0.0070	0.0098	0.0071	0.0077	0.0079
Inter-Instrument Variation	based on 30 tests	CV %	0.6	1.0	0.7	0.8	0.7
		SD	0.0103	0.0100	0.0092	0.0094	0.0097
inter-instrument variation	based on 6 tests	CV %	0.9	1.0	0.8	0.9	0.9
		SD	0.0144	0.0133	0.0130	0.0136	0.0136
	based on single tests	CV %	1.2	1.3	1.2	1.4	1.3
	between different days	SD	0.0054	0.0048	0.0055	0.0052	0.0052
	with each 6 tests	CV %	0.5	0.5	0.5	0.5	0.5
Typical within-instrument Variation (Median)	between single tests	SD	0.0113	0.0085	0.0097	0.0101	0.0099
	on one day	CV %	0.9	0.8	0.9	1.0	0.9
	between all tests	SD	0.0125	0.0097	0.0109	0.0111	0.0111
	on different days	CV %	1.0	1.0	1.0	1.1	1.0

	Ur	iformity					
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average
Average of Instruments (Grubbs)			83.713	80.255	79.466	77.662	
Reference Values for Evaluation			83.713	80.255	79.466	77.662	
Number Of Instruments			95	95	95	95	95
		SD	0.375	0.433	0.510	0.496	0.453
lakan la akunua ank Maniakian	based on 30 tests	CV %	0.4	0.5	0.6	0.6	0.6
		SD	0.479	0.519	0.569	0.557	0.531
Inter-Instrument Variation	based on 6 tests	CV %	0.6	0.6	0.7	0.7	0.7
		SD	0.687	0.684	0.754	0.771	0.724
	based on single tests	CV %	0.8	0.9	0.9	1.0	0.9
	between different days	SD	0.242	0.244	0.271	0.291	0.262
	with each 6 tests	CV %	0.3	0.3	0.3	0.4	0.3
Typical within-instrument Variation (Median)	between single tests	SD	0.511	0.478	0.538	0.539	0.516
	on one day	CV %	0.6	0.6	0.7	0.7	0.6
	between all tests	SD	0.565	0.512	0.592	0.613	0.570
	on different days	CV %	0.7	0.6	0.7	0.8	0.7

	Color Rd									
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average			
Average of Instruments (Grubbs)			77.855	75.111	70.625	76.781				
Reference Values for Evaluation			77.855	75.111	70.625	76.781				
Number Of Instruments			94	94	94	94	94			
		SD	0.462	0.331	0.420	0.399	0.403			
	based on 30 tests	CV %	0.6	0.4	0.6	0.5	0.5			
Inter-Instrument Variation		SD	0.482	0.365	0.453	0.425	0.431			
inter-instrument variation	based on 6 tests	CV %	0.6	0.5	0.6	0.6	0.6			
		SD	0.507	0.387	0.493	0.428	0.454			
	based on single tests	CV %	0.7	0.5	0.7	0.6	0.6			
	between different days	SD	0.154	0.120	0.135	0.132	0.135			
	with each 6 tests	CV %	0.2	0.2	0.2	0.2	0.2			
Typical within-instrument Variation	between single tests	SD	0.136	0.109	0.121	0.109	0.119			
(Median)	on one day	CV %	0.2	0.1	0.2	0.1	0.2			
	between all tests	SD	0.253	0.179	0.210	0.186	0.207			
	on different days	CV %	0.3	0.2	0.3	0.2	0.3			

Color +b										
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average			
Average of Instruments (Grubbs)			11.960	14.213	16.989	10.080				
Reference Values for Evaluation			11.960	14.213	16.989	10.080				
Number Of Instruments			94	94	94	94	94			
Inter-Instrument Variation		SD	0.280	0.242	0.349	0.211	0.271			
	based on 30 tests	CV %	2.3	1.7	2.1	2.1	2.0			
		SD	0.298	0.263	0.338	0.215	0.279			
inter-instrument variation	based on 6 tests	CV %	2.5	1.9	2.0	2.1	2.1			
		SD	0.321	0.278	0.343	0.236	0.294			
	based on single tests	CV %	2.7	2.0	2.0	2.3	2.2			
	between different days	SD	0.102	0.090	0.091	0.067	0.088			
Typical within-instrument Variation (Median)	with each 6 tests	CV %	0.9	0.6	0.5	0.7	0.7			
	between single tests	SD	0.090	0.064	0.072	0.063	0.072			
	on one day	CV %	0.8	0.4	0.4	0.6	0.6			
	between all tests	SD	0.159	0.123	0.141	0.110	0.133			
	on different days	CV %	1.3	0.9	0.8	1.1	1.0			

Optional Parameters

Inter-Instrument Averages, Inter-Instrument Variations, Typical within-instrument Variations


	Trash Count									
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average			
Average of Instruments (Grubbs)			26.94	10.75	10.50	17.80				
Reference Values for Evaluation			26.94	10.75	10.50	17.80				
Number Of Instruments			82	82	82	82	82			
Inter-Instrument Variation		SD	6.56	2.72	3.21	4.79	4.32			
	based on 30 tests	CV %	24.3	25.4	30.6	26.9	26.8			
		SD	7.05	2.98	3.30	5.06	4.60			
inter-instrument variation	based on 6 tests	CV %	26.2	27.7	31.4	28.4	28.4			
		SD	7.57	3.43	3.65	5.53	5.04			
	based on single tests	CV %	28.1	32.0	34.7	31.1	31.5			
	between different days	SD	2.50	1.08	1.01	1.68	1.57			
	with each 6 tests	CV %	9.3	10.1	9.7	9.4	9.6			
Typical within-instrument Variation (Median)	between single tests	SD	2.31	1.45	1.27	1.93	1.74			
	on one day	CV %	8.6	13.5	12.1	10.8	11.3			
	between all tests	SD	3.84	1.97	1.84	2.75	2.60			
	on different days	CV %	14.2	18.4	17.5	15.4	16.4			

	Trash Area										
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average				
Average of Instruments (Grubbs)			0.254	0.114	0.108	0.182					
Reference Values for Evaluation			0.254	0.114	0.108	0.182					
Number Of Instruments			82	82	82	82	82				
Inter-Instrument Variation		SD	0.056	0.025	0.024	0.048	0.038				
	based on 30 tests	CV %	22.1	22.2	21.9	26.3	23.1				
		SD	0.065	0.026	0.031	0.055	0.044				
inter-instrument variation	based on 6 tests	CV %	25.7	22.7	28.4	30.5	26.8				
		SD	0.089	0.031	0.033	0.061	0.053				
	based on single tests	CV %	34.9	27.3	30.3	33.5	31.5				
	between different days	SD	0.032	0.013	0.013	0.026	0.021				
	with each 6 tests	CV %	12.6	11.4	12.2	14.3	12.6				
Typical within-instrument Variation (Median)	between single tests	SD	0.027	0.014	0.014	0.025	0.020				
	on one day	CV %	10.8	12.0	12.5	13.9	12.3				
	between all tests	SD	0.043	0.022	0.024	0.039	0.032				
	on different days	CV %	16.7	19.8	22.2	21.6	20.1				


	M	aturity					
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average
Average of Instruments (Grubbs)			85.53	86.52	84.16	85.31	
Reference Values for Evaluation			85.53	86.52	84.16	85.31	
Number Of Instruments			73	73	73	73	73
		SD	0.54	0.50	0.62	0.57	0.56
Inter-Instrument Variation	based on 30 tests	CV %	0.6	0.6	0.7	0.7	0.7
		SD	0.55	0.50	0.58	0.60	0.56
inter-instrument variation	based on 6 tests	CV %	0.6	0.6	0.7	0.7	0.7
		SD	0.60	0.56	0.71	0.64	0.63
	based on single tests	CV %	0.7	0.7	8.0	8.0	0.7
	between different days	SD	0.09	0.08	0.07	0.09	0.08
	with each 6 tests	CV %	0.1	0.1	0.1	0.1	0.1
Typical within-instrument Variation (Median)	between single tests	SD	0.12	0.09	0.11	0.14	0.12
	on one day	CV %	0.1	0.1	0.1	0.2	0.1
	between all tests	SD	0.19	0.18	0.18	0.25	0.20
	on different days	CV %	0.2	0.2	0.2	0.3	0.2

		SFI					
			Cotton 1	Cotton 2	Cotton 3	Cotton 4	Average
Average of Instruments (Grubbs)			7.12	11.84	11.98	15.65	
Reference Values for Evaluation			7.12	11.84	11.98	15.65	
Number Of Instruments			85	85	85	85	85
Inter-Instrument Variation		SD	0.82	1.25	1.24	1.97	1.32
	based on 30 tests	CV %	11.5	10.6	10.4	12.6	11.2
		SD	0.84	1.30	1.30	2.02	1.36
	based on 6 tests	CV %	11.8	10.9	10.8	12.9	11.6
		SD	0.91	1.43	1.44	2.17	1.49
	based on single tests	CV %	12.8	12.0	12.0	13.8	12.7
	between different days	SD	0.18	0.33	0.33	0.38	0.31
	with each 6 tests	CV %	2.6	2.8	2.7	2.4	2.6
Typical within-instrument Variation (Median)	between single tests	SD	0.39	0.57	0.58	0.75	0.57
	on one day	CV %	5.4	4.8	4.9	4.8	5.0
	between all tests	SD	0.41	0.64	0.65	0.87	0.64
	on different days	CV %	5.8	5.4	5.4	5.5	5.5


Test Result Distributions Micronaire

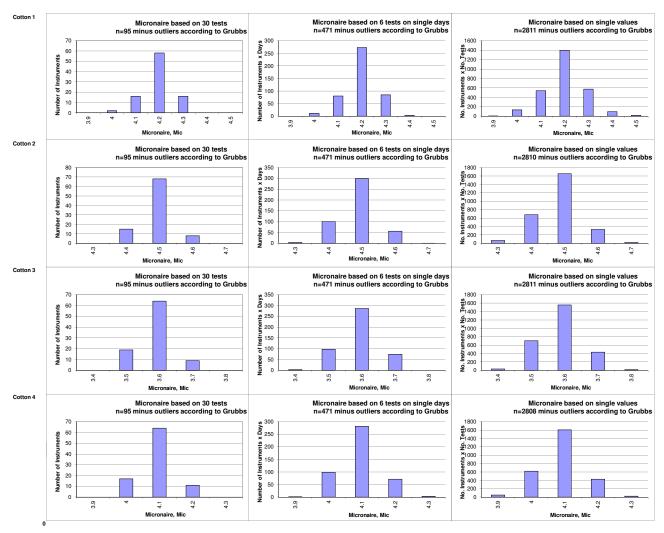


Test Result Distributions Strength

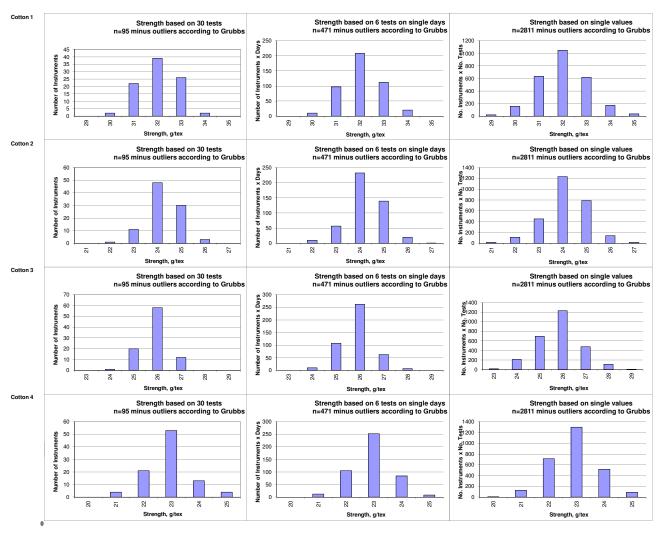


Test Result Distributions Length

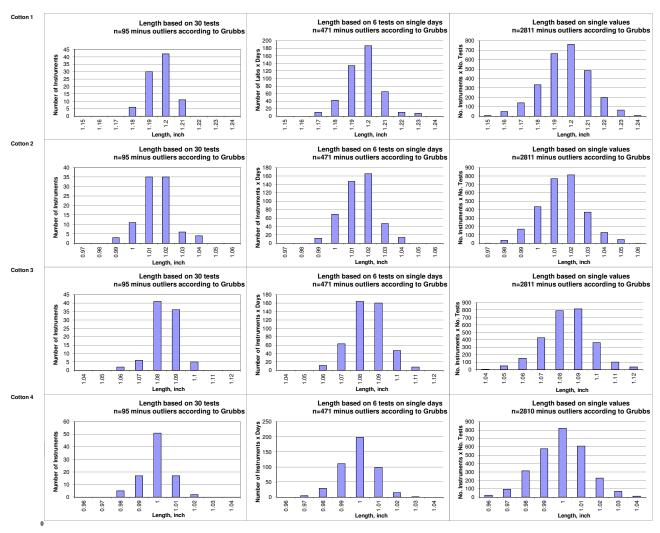


Test Result Distributions Uniformity

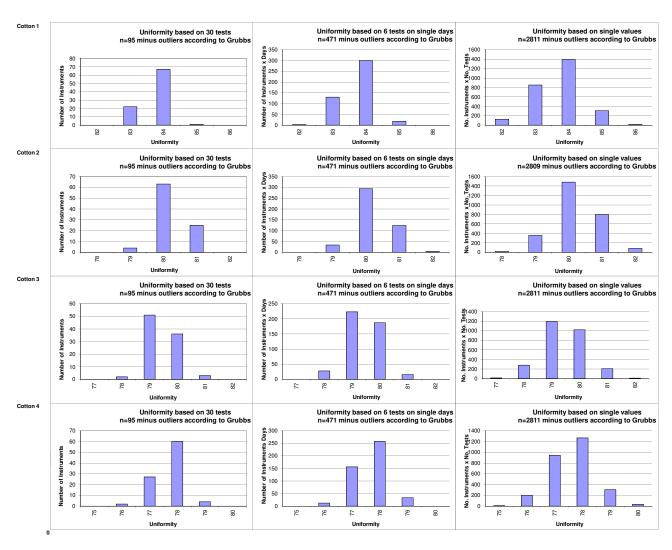


Test Result Distributions Color Rd

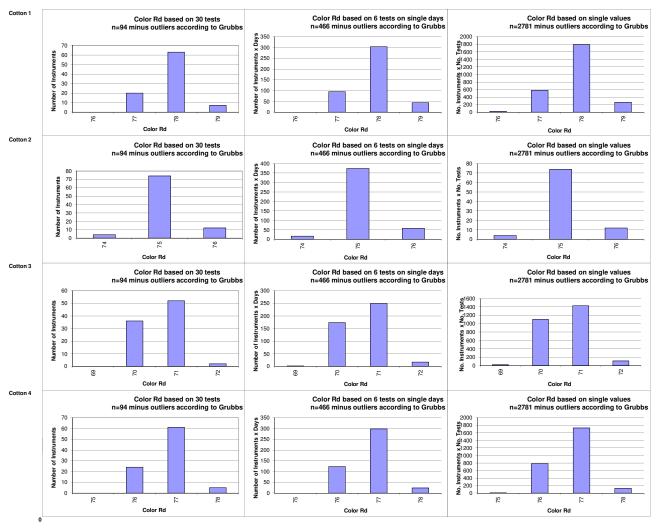


Test Result Distributions Color +b

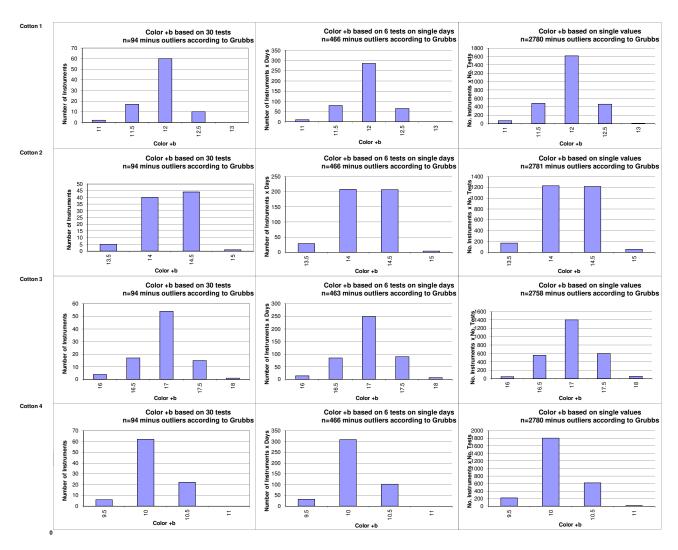


Test Result Distributions Trash Count

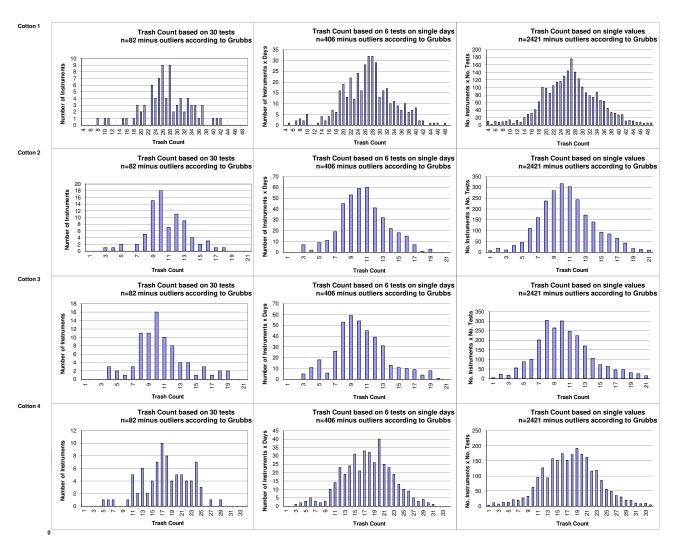


Test Result Distributions Trash Area

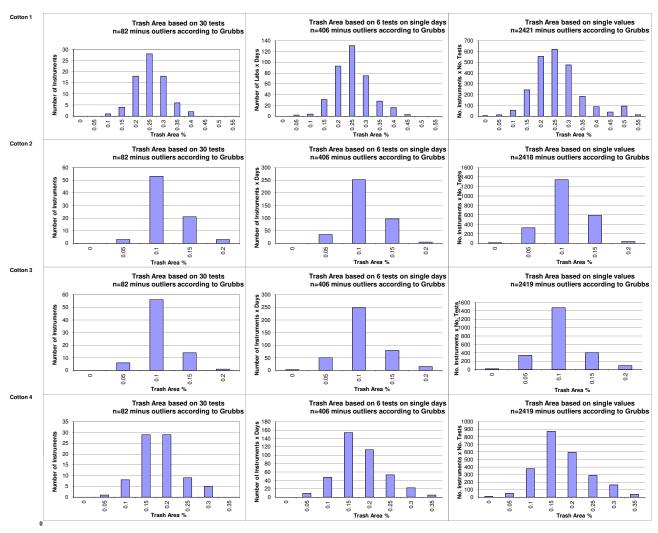

Test Result Distributions Maturity

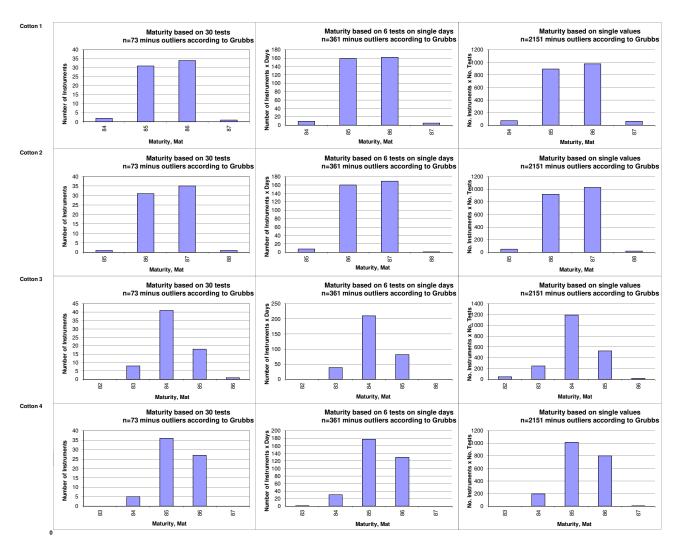

Test Result Distributions SFI

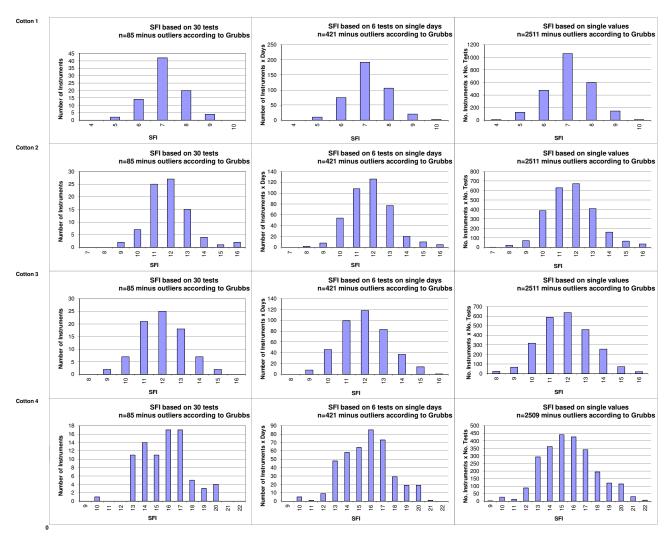



International Cotton Advisory Committee



CSITC Global - Round Trial 2021 - 2 General Evaluation

Section One: Result Distribution

Section Two: Instrument Evaluation

Section Three: Within Limits Evaluation

Section Two: Instrument Evaluation

Content:

- -Evaluation of Combined Parameters
- -Evaluation of Single Parameters

Executed By: Faserinstitut Bremen e.V., Bremen, Germany* USDA-AMS, Memphis, TN, USA System Provided by: Generation 10 Limited



This report is an outcome of the Project CFC/ICAC/33 – CSITC, which benefitted from support from the Common Fund for Commodities and the European Union, partners in Commodity Development.




Instrument Evaluation

- Graph of Combined Properties -

According to ICAC CSITC Task Force Recommendations

Global - Round Trial 2021 - 2

		Evaluation Combined Prop.
Statistics	Average	0.45
	Median	0.31
	Best Instrument	0.17
	Worst Instrument	4.59

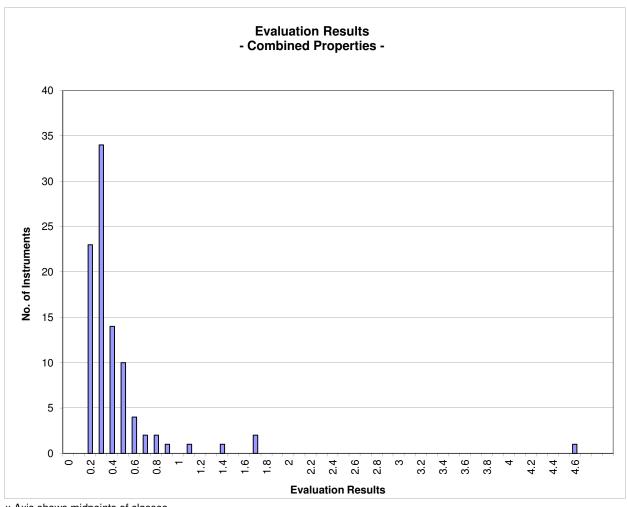

x-Axis shows midpoints of classes

The evaluation results are entered based on the unrounded values (classes are defined as > lower limit and <= upper limit)


Instrument Evaluation

- Graph of Single Properties -

According to ICAC CSITC Task Force Recommendations

Global - Round Trial 2021 - 2

		Evaluation Micronaire		Evaluation Length	Evaluation Uniformity	Evaluation Color Rd	Evaluation Color +b
Statistics	Average	0.49	0.43	0.41	0.44	0.28	0.60
	Median	0.35	0.32	0.27	0.27	0.20	0.37
	Best Instr.	0.09	0.03	0.08	0.04	0.03	0.06
	Worst Instr.	4.52	2.75	4.79	4.46	2.94	9.57

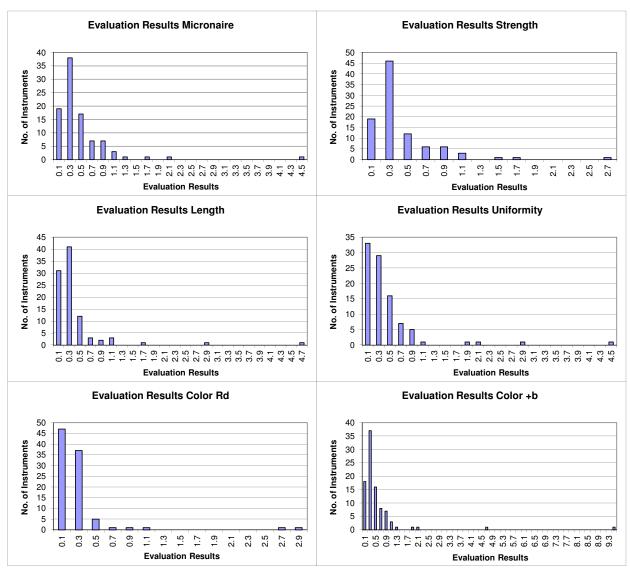

x-Axis shows midpoints of classes

The evaluation results are entered based on the unrounded values



International Cotton Advisory Committee



CSITC Global - Round Trial 2021 - 2 General Evaluation

Section One: Result Distribution Section Two: Instrument Evaluation Section Three: Within Limits Evaluation

Section Three: Within Limits Evaluation

Content:

- -Based on Average of 30 Test Results
- -Based on Single Test Results

Executed By:
Faserinstitut Bremen e.V., Bremen, Germany*
USDA-AMS, Memphis, TN, USA

System Provided by: Generation 10 Limited



This report is an outcome of the Project CFC/ICAC/33 – CSITC, which benefitted from support from the Common Fund for Commodities and the European Union, partners in Commodity Development.



Within Limits Evaluation

Based on average of 30 test results for each sample

	Micronaire	Strength	Length	Uniformity	Color Rd	Color +b
Limits	0.20	2.0	0.030	2.0	1.5	0.5
	units	g/tex	inch	%	units	units
Average % Results within Limits	97.9	96.6	98.2	97.6	97.1	89.1
Completely within limits	96.8	91.6	95.8	95.8	95.7	78.7
% of Instruments ≥75% within limits	96.8	96.8	97.9	97.9	95.7	88.3
% of Instruments ≥50% within limits	98.9	97.9	98.9	97.9	97.9	93.6

Within Limits Evaluation

Based on Single Test Results

	Micronaire	Strength	Length	Uniformity	Color Rd	Color +b
Limits	0.20	2.0	0.030	2.0	1.5	0.5
	units	g/tex	inch	%	units	units
Average % Results within Limits	97.2	93.1	95.7	96.3	95.8	85.6
% of Instruments 100% within limits	68.4	32.6	37.9	53.7	80.9	36.2
% of Instruments ≥95% within limits	90.5	73.7	84.2	92.6	89.4	57.4
% of Instruments ≥75% within limits	96.8	92.6	96.8	96.8	94.7	80.9
% of Instruments ≥65% within limits	96.8	95.8	97.9	96.8	94.7	86.2
% of Instruments ≥50% within limits	98.9	97.9	97.9	97.9	97.9	91.5